

This is the draft manuscript of the following publication:

The effect of critical micelle concentration on the amphiphilic species response using P3HT-based organic electrochemical transistors

Tatiana Gregorio, Iris Miraballes, Dominique Mombrú, Mariano Romero, Alvaro W Mombrú

Journal of Materials Chemistry C 2025, 13, 36, 18724-18733.

Publisher: The Royal Society of Chemistry

The effect of critical micelle concentration on the amphiphilic species response using P3HT-based organic electrochemical transistors

Tatiana Gregorio¹, Iris Miraballes^{2,3}, Dominique Mombrú^{*1}, Mariano Romero^{*1}, Alvaro W. Mombrú^{*1}.

1 Centro NanoMat & Área Física, Departamento de Experimentación y Teoría de la Estructura de la Materia y sus Aplicaciones (DETEMA), Facultad de Química, Universidad de la República, Montevideo C.P. 11800, Uruguay.

2 Inmunología Clínica (BIOCLIN), Facultad de Química, Universidad de la República, Montevideo C.P. 11800, Uruguay.

3 Laboratorio de Biotecnología (Instituto Polo Tecnológico de Pando), Facultad de Química, Universidad de la República, Canelones C.P. 91000, Uruguay.

* Corresponding authors:

Dr. Dominique Mombrú (dmombbru@fq.edu.uy)

Dr. Mariano Romero (mrromero@fq.edu.uy)

Dr. Alvaro W. Mombrú (amombbru@fq.edu.uy)

Abstract

Here, we present a proof-of-concept approach to study the effect of critical micelle concentration on alkyl sulfonate amphiphilic species response using organic electrochemical transistors (OECT) working in the accumulation mode. First of all, the drastic enhancement of the OECT response allows us to estimate the critical micelle concentration of alkyl sulfonate amphiphilic species yielding quite similar values compared to bulk solution conductivity experiments reported in the literature. Above the critical micelle concentration (*i.e.* 100 mM), the best responsive OECT devices yielded ON/OFF ratios of 30 – 60, maximum normalized transconductance of $g_{\max}^* = 1.99 - 1.39 \text{ mS.cm}^{-1}$ and threshold voltage of $-V_{\text{th}} = 0.39 - 0.55 \text{ V}$ at $V_g = -1.0 \text{ V}$. Our impedance spectroscopy studies performed at ON and OFF modes suggested that, in the presence of a sufficiently strong negative gate voltage ($V_g = -1.0 \text{ V}$), not only the sodium counterions are ejected from the interface, but also the amphiphilic molecules from the monolayer probably reverse their orientation and get injected into the P3HT region. In this scenario, the sulfonate groups of the amphiphilic species synchronously induce doping of P3HT thus leading to a drastic enhancement of the channel current above the critical micelle concentration. Our results indicate that OECT devices represent a promising platform to estimate the critical micelle concentration of amphiphilic species but also to study the formation of amphiphilic monolayers of more complex systems of biological interest.

Keywords: OECT, P3HT, amphiphilic species, critical micelle concentration, alkyl sulfonate.

1. Introduction

Organic electrochemical transistors (OECTs) are one of the most promising sensing devices that can operate in aqueous media and are particularly interesting for transducing and amplifying low-amplitude ionic fluctuations of biological interest.¹ The OECTs can operate in depletion (*i.e.* the positive biasing of the gate electrode introduces cations into the semiconducting polymer leading to a decrease in the channel current) or accumulation (*i.e.* the negative biasing of the gate electrode introduces anions into the semiconducting polymer leading to an increase in the channel current) mode. The corresponding most frequent materials used as a channel for each working mode are poly(3,4-ethylenedioxythiophene) doped with poly(styrenesulfonate) (PEDOT:PSS)²⁻⁴ and the undoped poly(3-hexylthiophene) (P3HT) and all its glycolated side chain analogs^{5,6}, respectively. Particularly, the use of P3HT without glycolated side chain modification as channel materials is usually reserved for electrolyte-gated organic field-effect transistors (EGOFET) rather than an OECT considering its hydrophobic nature.⁷⁻¹² However, although P3HT swelling abilities are limited compared to its glycolated side chain analogs, there are a lot of studies suggesting that charge transport and transfer processes are far from being only a simple interface phenomenon. Huang *et al.* have reported that they produce P3HT porous films with controlled morphologies without the aid of polymer additives, enhancing OECT properties for hydrophobic polymers with efficient doping, fast ion intercalation/de-intercalation, high transconductance and capacitance¹³. The performance of P3HT-based OECTs has been improved by the preparation of a nanofiber microstructure, not only offering a porous interface with electrolytes but also promoting efficient ionic penetration and doping of the conjugated polymers¹⁴. The ionic fluctuations of biological origin refer to basic physiological indicators such as body temperature, blood pressure, blood oxygen levels, and heart rate, but can also refer to clinically relevant disease-specific biomolecules such as nucleic acid fragments, proteins, and metabolic molecules.^{15,16} The most studied analytes using OECT devices working in depletion or accumulation mode are typically hydrophilic, *e.g.* simple ionic species such as hydronium, sodium, potassium, fluoride, chloride and bromide,^{17,18} metabolites such as lactic acid¹⁹⁻²¹, ascorbic acid²², sialic acid²³⁻²⁵, uric acid²⁶⁻²⁸, hormones such as epinephrine²⁹⁻³¹, neurotransmitters such as dopamine and acetylcholine³²⁻³⁴ and more complex systems such as deoxyribonucleic acid and proteins.³⁵⁻³⁸ However, other metabolites of biological interest with hydrophobic nature have been much

less explored. For instance, an OECT-based electrochemical sensor for the selective detection of Vitamin A in the form of retinyl acetate has been reported recently but using an organic electrolytic solution.³⁹ In between, there are other metabolites with an amphiphilic nature such as surfactants but also the particular case of fatty acids and their corresponding salts that are extremely relevant in different biological processes have not been studied yet. An amphiphilic compound is a term used to describe a compound containing a large organic cation or anion that possesses a long unbranched hydrocarbon chain. The existence of distinct polar (hydrophilic) and nonpolar (hydrophobic) regions in the molecule promotes the formation of micelles in aqueous solution.⁴⁰ In addition, it is well known that the amphiphilic species form these micelles above a certain concentration [*i.e.* the critical micelle concentration (c.m.c.)] while the amphiphilic species are more or less isolated in the diluted regime. The c.m.c. determination of amphiphilic species in bulk solutions has been typically studied by conductivity, surface tension, fluorescence and dynamic light scattering measurements.⁴¹ Furthermore, the formation of micelles above the critical micelle concentration is accompanied by the formation of monolayers at both air and electrode interfaces. In the case of solid-liquid interfaces, not only monolayers and bilayers but a wide variety of surface micelles on solid surfaces have been found, such as hemicylinders, cylinders, hemispheres, and spheres.⁴² Here, typical experimental methodologies include direct observation using atomic force microscopy (AFM) but also electrophoretic light scattering (ELS), which offers a rapid, high-resolution technique for the study of a wide variety of samples but not so straightforward for small micelles of surfactants whose sizes are in the range of only a few nanometers.⁴² The use of self-assembled lipid bilayers on PEDOT:PSS-based electrodes and transistors as promising platforms for biosensing purposes has been reported recently⁴³⁻⁴⁵, but in the case of P3HT-based transistors, only chemically bonded lipid monolayers have been studied.^{46,47} However, the later cases only use the amphiphilic species as biocompatible platforms to sense different metabolites but, to the best of our knowledge, there have been no approaches to studying the interaction and detection of amphiphilic species with P3HT using organic electrochemical transistors. Here, we present a proof-of-concept approach to study the effect of critical micelle concentration on the amphiphilic species response using a P3HT-based OECT working in the accumulation mode.

2. Methodology

2.1 Preparation of OECT devices

The OECT devices with coplanar geometry were prepared using thin gold gate, source and drain electrodes which were sputtered onto a glass substrate in a 0.2 mbar argon atmosphere at 30 mA DC sputtering ion current for 300 s using a removable insulating polymeric template (Scotch® Magic™ Tape 810HK) defining a channel area with length $L \sim 20 \mu\text{m}$ and widths $W \sim 1000 \mu\text{m}$. Then, 5 μL of P3HT (SIGMA-ALDRICH CAS 104934-50-1: regioregular > 90%, average Mw 50.000–75.000) dissolved in toluene with 10 mg/ml concentration was deposited on the channel area and dried at 100 °C for 60 minutes, yielding a thickness $d \sim 2 \mu\text{m}$. It is important to note that the OECT channel thickness is relatively high compared to typical values reported in the literature (*e.g.* 0.1 to 1.4 μm).⁴⁸⁻⁵⁰ However, as we have no prior information about amphiphilic species interaction with P3HT-based OECTs, the use of thicker films can be justified by favoring the expected enhancement of transconductance at the expense of response times declining, as already observed in the literature for both hydrophobic and hydrophilic cases.⁴⁸⁻⁵⁰ The same insulating polymeric mask was then deposited, leaving only the channel and gate area exposed to different amphiphilic electrolyte solutions based on the sodium alkyl sulfonates $\text{C}_n\text{H}_{2n+1}\text{SO}_3\text{Na}$ ($n = 4, 6, 8, 10$ and 12) with concentrations ranging from 1 to 100 mM, as schematized in **Figure S1**. In addition, sodium lauryl sulfate ($\text{C}_{12}\text{H}_{25}\text{SO}_4\text{Na}$) was also studied to evaluate the role of amphiphilic head groups and sodium chloride (NaCl) was studied to evaluate the role of ionic strength. All the electrolyte salts were provided by SIGMA-ALDRICH and used without prior purification.

2.2 Characterization of OECT devices

The P3HT films comprising the OECT devices were characterized using grazing incidence small- and wide-angle X-ray scattering and microRaman imaging, as detailed and depicted in **Figure S2** and **Figure S3**, respectively. The hydrodynamic diameter and zeta potential of the amphiphilic electrolytes were determined using the particle size/zeta potential analyzer Nano-ZS (Malvern Instruments Ltd.) in an aqueous medium at 25 and 30 °C, for $n = 10$ and 12 , respectively.

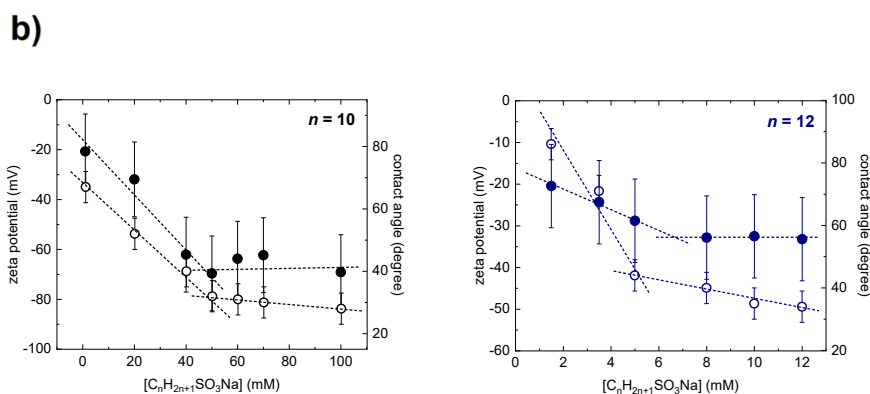
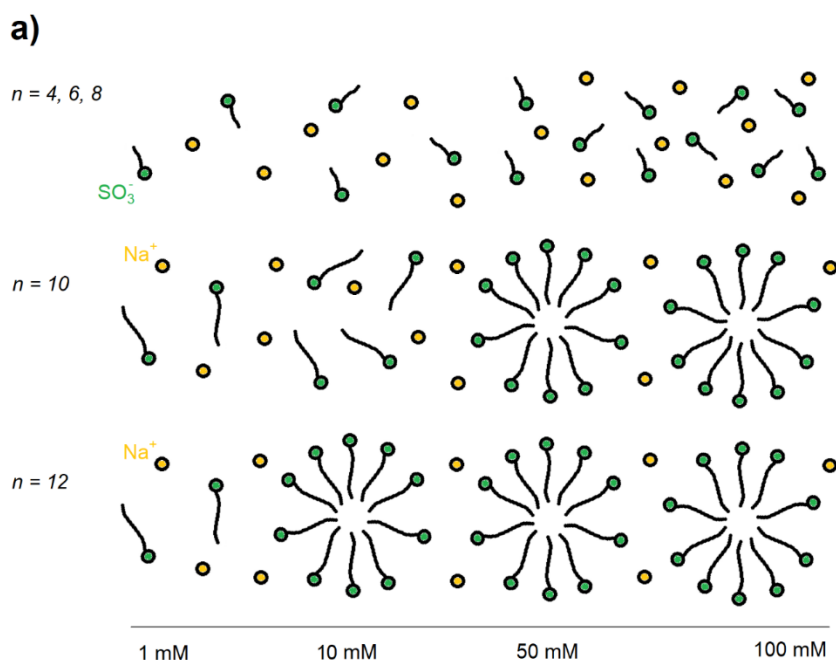



Figure 1 – a) Schematization of critical micelle concentration for $\text{C}_n\text{H}_{2n+1}\text{SO}_3\text{Na}$ ($n = 4, 6, 8, 10$ and 12) and **b)** zeta potential (full circles) and contact angle (hollow circles) at different $\text{C}_n\text{H}_{2n+1}\text{SO}_3\text{Na}$ concentrations for $n = 10$ and 12 , at 25 and 30 °C, respectively.

The hydrodynamic diameter was evaluated using dynamic light scattering (DLS) and reported as the z-average, while zeta potential was calculated from the electrophoretic mobility using the Helmholtz–Smoluchowski equation. The contact angle measurements were performed using the Sessile Drop Method. Each sample was analyzed in triplicate. X-ray reflectometry (XRR) was performed using Rigaku Ultima IV diffractometer with Cu K α radiation working in parallel beam configuration. XRR patterns were used to estimate the critical angle and rugosity of P3HT films exposed to electrolytes below and above the critical micelle concentration. The channel current (I_{ds}) for our OECT devices was collected between the source and drain


electrodes in the $V_{ds} = -1.0 \text{ V} - 0.0 \text{ V}$ drain-source voltage range and different applied gate voltages between the gate and the source electrodes in the $V_g = -1.0 \text{ V} - 0.0 \text{ V}$ range using the Keithley 2450 source-meter. In each case, the gate voltages were applied for several minutes to assure equilibrium conditions before each measurement, and then each output data point was collected for 240 seconds until current stabilization. Impedance spectroscopy data were also collected between the gate and short-circuited source-drain electrodes of the OECT devices using Gamry Reference 3000 galvanostat/potentiostat working with an AC voltage amplitude of $V_{g,ac} = 20 \text{ mV}$ in the $0.1 \text{ Hz} - 100 \text{ kHz}$ frequency range at the OFF ($V_{g,dc} = 0.0 \text{ V}$) and ON ($V_{g,dc} = -1.0 \text{ V}$) modes. All electrical characterizations were performed inside an isolated Faraday cage at 25°C and 50% RH ambient conditions.

3. Results and discussion

First of all, it is important to mention that the solubility of $C_nH_{2n+1}SO_3Na$ ($n = 4, 6, 8$ and 10) aqueous electrolytes was observed below 100 mM concentrations for all amphiphilic species at 25°C . The c.m.c. reported for $C_nH_{2n+1}SO_3Na$ ($n = 4, 6, 8, 10$ and 12) aqueous solutions at room temperature is c.m.c. $\sim 8 - 10 \text{ mM}$ for $n = 12$, $\sim 43 - 45 \text{ mM}$ for $n = 10$, and above 100 mM for $n < 10$, according to the literature⁴¹, as schematized in **Figure 1a**. Our dynamic light scattering experiments corroborate the formation of micelles with a corresponding hydrodynamic mean size between $\sim 2.1 - 3.0 \text{ nm}$, and the zeta potential exhibited a crossover at $\sim 5 - 8 \text{ mM}$ for $n = 12$ and at $\sim 40 - 50 \text{ mM}$ for $n = 10$, in good agreement with the bulk solution c.m.c. values, as depicted in **Figure 1b**. It is important to mention that the larger size region was omitted for clarity and that both the hydrodynamic mean size and zeta potential are quite expected in comparison with those reported in the literature.⁵¹ X-ray reflectometry (XRR) profiles of P3HT films exposed at different $C_nH_{2n+1}SO_3Na$ concentrations for $n = 10$ and 12 , at 25 and 30°C , respectively, are depicted in the upper panel of **Figure 2**. The critical angle observed at $\theta_c \sim 0.46^\circ$ is mostly associated with the silicate glass substrate and the critical angle of P3HT film is probably masked at lower angles, as already observed for similar cases in the literature.⁵² However, the smoothness of the XRR profile indicates that the film thickness is not thin enough, *i.e.* $\sim 2 \mu\text{m}$ according to our Raman imaging analysis displayed in **Figure S3**, to define the typical Kiessing fringes oscillation patterns observed for thinner films.⁵³

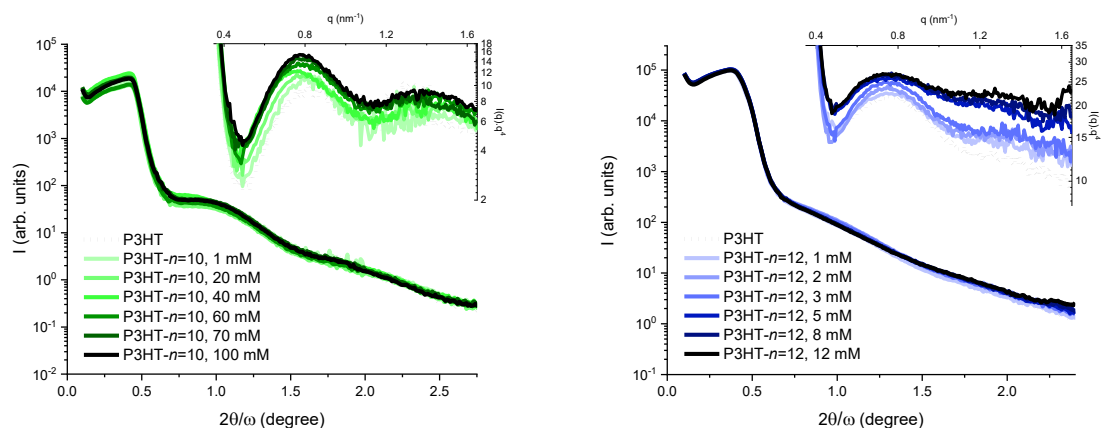

$n = 10$

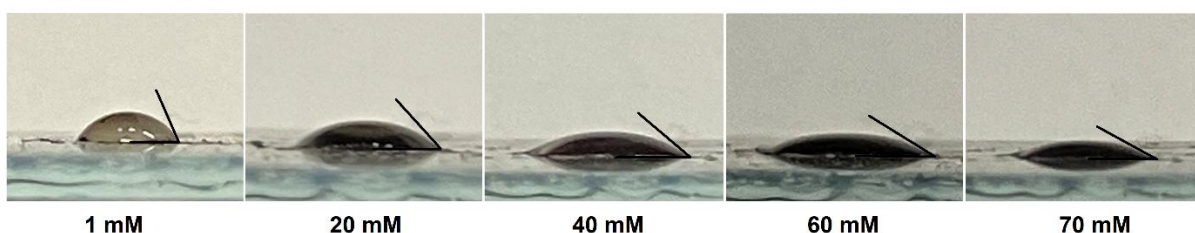

$n = 12$

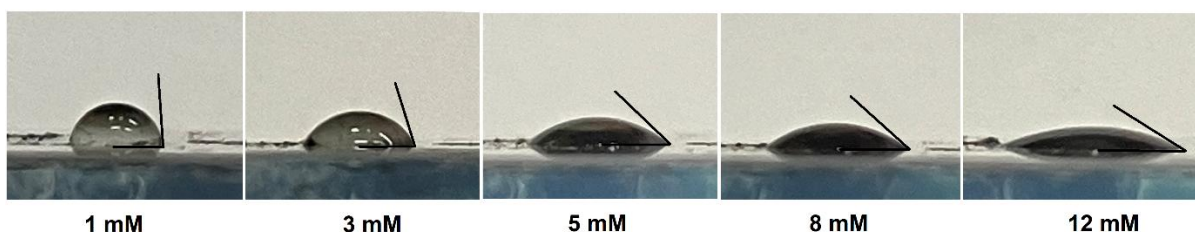


Figure 2 – X-ray reflectometry (XRR) curves depicted as $I(q)$ vs $2\theta/\omega$ and $I(q) \cdot q^4$ vs q plots (upper panel) and contact angle images (lower panel) for P3HT films exposed at different $C_{nH_{2n+1}SO_3Na}$ concentrations for $n = 10$ and 12 , at 25 and 30 °C, respectively.

In order to have more fine detail of X-ray reflectometry analysis, the $I(q) \cdot q^4$ vs q plots are plotted and analyzed. The presence of broad oscillations that are frequently associated with ultrathin layers (*i.e.* < 3 nm) is observed for all cases and a clear shift toward lower q values is progressively observed with increasing amphiphilic species concentration until almost stabilized at ~ 40 mM (for $n = 10$) and at ~ 5 mM (for $n = 12$), in good agreement with bulk solution c.m.c. values. Although the data does not allow the confirmation of the formation of a well-defined monolayer, the formation of a stabilized ultrathin layer comprised of amphiphilic species above the P3HT film is in good agreement with the formation of micelles

observed for bulk solution experiments discussed earlier. The contact angle images for P3HT films exposed at different $C_nH_{2n+1}SO_3Na$ concentrations for $n = 10$ and 12, at 25 and 30 °C, respectively, are shown in the lower panel of **Figure 2**. The contact angles showed a marked decrease from $\sim 67^\circ$ at 1 mM until stabilized on $\sim 30^\circ$ at ~ 40 mM (for $n = 10$) and showed a marked decrease from $\sim 86^\circ$ at 1 mM until stabilized on $\sim 40^\circ$ at ~ 5 mM (for $n = 12$), as depicted in **Figure 1b**, in agreement with the formation of micelles observed for bulk solution experiments discussed earlier.

The output characteristics collected at fixed $V_{ds} = -0.8$ V and $V_g = -1.0$ V for P3HT-based OEET working with $[C_nH_{2n+1}SO_3Na]$ with $n = 4, 6, 8, 10$ and 12 at different electrolyte concentrations ranging between 1 – 100 mM at 25 °C are displayed in the left panel of **Figure 3**. It is quite interesting to note that, while $n < 10$ species exhibit a soft increase in $-I_{ds}$ with increasing concentration, $n = 10$ exhibits a sudden notorious increase in $-I_{ds}$ just above the c.m.c. (*i.e.* ~ 50 mM).

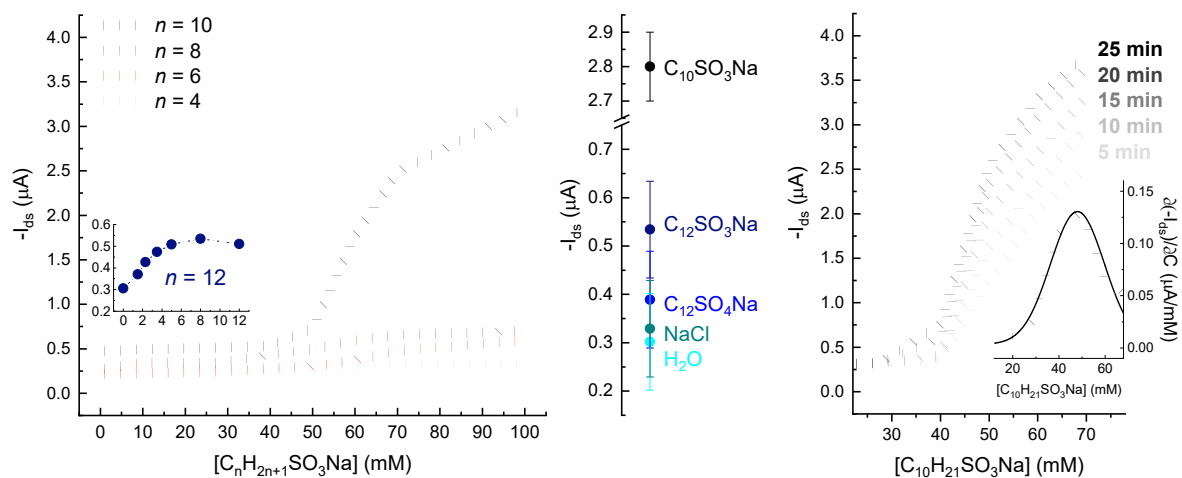


Figure 3 – Output data collected at fixed $V_{ds} = -0.8$ V and $V_g = -1.0$ V for P3HT-based OEET working with $C_nH_{2n+1}SO_3Na$ with $n = 4, 6, 8, 10$ and 12 at different electrolyte concentrations ranging between 1 – 100 mM at 25 °C (left panel), working with $C_{12}H_{25}SO_3Na$ and $C_{12}H_{25}SO_4Na$ just above their c.m.c. (*i.e.* $\sim 8 - 10$ mM), $NaCl$ at 10 mM and distilled water at 25 °C (middle panel) and working with $n = 10$ at different stabilization times and the corresponding first derivative for stabilized data at 25 °C (right panel).

In the case of $n = 12$, we also observed a sudden but less marked increase just below its corresponding c.m.c., *i.e.* $\sim 4 - 6$ mM. However, it is important to mention that this value is shifted to lower values compared to literature (*i.e.* $\sim 8 - 10$ mM)⁴¹ as similarly observed for $n = 12$ when interacting with polymers in solution.⁵¹ Interestingly, n -alkyl sulfonates with shorter alkyl chains, such as $n = 10$, do not exhibit drastic shifting of c.m.c. when interacting with polymers in solution.⁵¹ In addition, it is also important to note that the OECT response for $n = 12$ exhibited considerably lower channel current values above c.m.c. compared to those observed for $n = 10$. This suggests that the amphiphilic species c.m.c. value strongly affects the OECT response and, particularly, those with higher c.m.c values exhibited a more marked response. In addition, we also plot the $-I_{ds}$ values obtained at fixed $V_{ds} = -0.8$ V and $V_g = -1.0$ V for sodium lauryl sulfonate ($C_{12}H_{25}SO_3Na$) and sulfate ($C_{12}H_{25}SO_4Na$) near above their c.m.c. (*i.e.* $\sim 8 - 10$ mM) to evaluate the role of different amphiphilic head groups, as shown in the middle panel of **Figure 3**. It is observed that the electrolyte response is higher for sodium lauryl sulfonate ($C_{12}H_{25}SO_3Na$) compared to sodium lauryl sulfate ($C_{12}H_{25}SO_4Na$). This difference can be related to the higher oxidant properties of sulfonate with respect to sulfate head groups, considering that both species present the same alkyl chain and very similar c.m.c. values. However, it is important to note that their $-I_{ds}$ values are slightly higher compared to NaCl 10 mM aqueous solution, indicating that the doping abilities of amphiphilic species with lower c.m.c. values (such as $n = 12$ alkyl sulfonates) are comparable to the effect of ionic strength and, thus, are much poorer than those with higher c.m.c values (such as $n = 10$ alkyl sulfonates). The right panel of **Figure 3** shows the output characteristic data collected for $n = 10$ electrolyte in the same conditions as mentioned earlier at different stabilization times, indicating that the OECT reaches stable values after 25 minutes. These relatively long stabilization times probably refer to the slow formation kinetics of the amphiphilic species monolayer on the polymeric surface, but also to the slow ionic diffusion kinetics when injected into the conducting polymer. Furthermore, this is relevant to obtain more accurate values for the critical micelle concentration by using the first derivative maximum, yielding c.m.c. = (48.0 ± 1.8) mM. Similarly, but not shown in the figure, the c.m.c. for $n = 12$ electrolyte estimated using the same procedure yielded c.m.c. = (3.6 ± 0.7) mM. Here, we are demonstrating that our c.m.c. estimation using a P3HT-based OECT device yielded quite similar values compared to bulk solution conductivity experiments reported in the literature.⁴¹

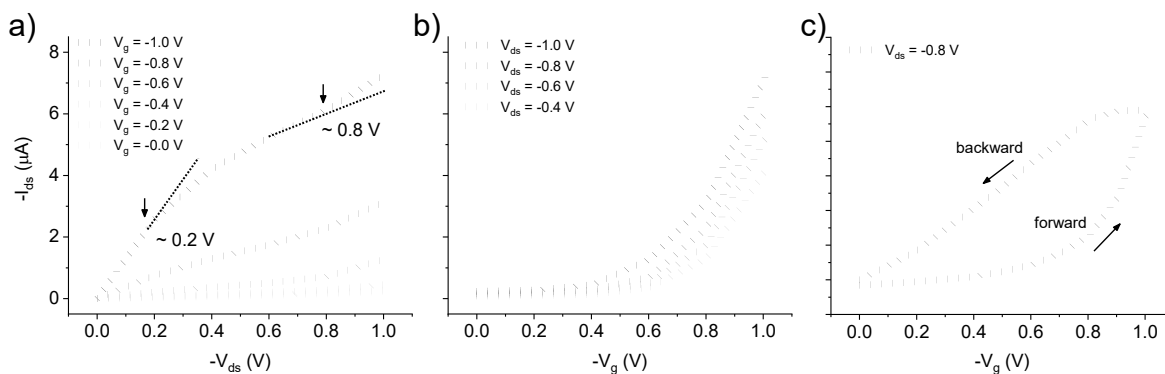


Figure 4 – a) Output ($-I_{ds}$ vs $-V_{ds}$ at selected V_g values), **b)** transfer ($-I_{ds}$ vs $-V_g$ at selected V_{ds} values) and **c)** hysteresis transfer ($-I_{ds}$ vs $-V_g$ at selected V_{ds} value in forward and backward directions) characteristics for P3HT-based OECT working with $[C_{10}H_{21}SO_3Na]$ 0.1 M electrolyte at 25 °C. The voltages at which the transistor output characteristic switches from linear to quasi-saturation regime are marked with arrows.

It is noteworthy to mention that in these cases, we are obtaining information not only about the micelle but also about the monolayer formed at the interface with the conductive polymer. We expanded the characterization of OECT devices working with the more sensitive electrolyte above the c.m.c. to evaluate the micelle and monolayer effect on the OECT response. Thus, the corresponding output, transfer and hysteresis transfer characteristics for P3HT-based OECT working with $n = 10$ electrolyte at 25 °C above its c.m.c. value; *i.e.* 0.1 M, are shown in **Figure 4**. The output and transfer characteristics, as well as the transconductance and threshold voltage plots for P3HT-based OECT working with $n = 12$ electrolyte at 30 °C just above its c.m.c. value; *i.e.* 8 mM, are shown in **Figure S4**. It is important to note that the output characteristic showed a deviation from the typical saturation behavior, as already observed to be especially prevalent in hydrophobic materials with alkyl side chains.⁵⁴⁻⁵⁶ This deviation can probably be associated with a spatially non-uniform hole mobility throughout the volume of the channel with regard to the transistor pinch-off operating in a mixed OECT/EGOFET regime.¹⁷ In fact, for $n = 10$, the transistor output characteristic switches from a linear regime at $V_{ds} \sim -0.2$ V but only reaches a quasi-saturation regime at $V_{ds} \sim -0.8$ V, which could be considered an underestimation of the pinch-off voltage, as depicted in **Figure 4a**. For $n = 10$ above c.m.c., the transfer characteristics exhibited $-I_{ds, V_g=-1.0V}$ values ranging from 7.26, 6.12, 5.24 and 4.20 μA and ON/OFF ratios (estimated using the $-I_{ds, V_g=-1.0V}/-I_{ds, V_g=0.0V}$ ratio) ranging

from 32, 39, 47 and 60 for $V_{ds} = -1.0, -0.8, -0.6$ and -0.4 V, respectively. The transfer hysteresis curve of the OECT devices evidenced a notorious difference between forward and backward transfer characteristics. Typically, P3HT-based OECT devices exhibited a capacitive hysteresis behavior described by the higher absolute values of the current in the backward direction with respect to the forward direction.⁵⁷ However, the great difference between forward and backward transfer characteristics is expected for such a large anion with limiting ionic transport.⁵⁷ It is important to note that the transfer hysteresis curve was collected using a slow scan rate (~ 0.5 mV/s) to minimize the contribution to the hysteresis behavior due to fast scan rates. The hysteresis behavior can thus be attributed mostly to the slow ionic injection/ejection dynamics and the limitations of ion diffusion kinetics.⁵⁷ The transconductance (g_m) defined as $g_m = |\partial I_{ds}/\partial V_g|$ and the square root current ($|I_{ds}|^{1/2}$) as a function of V_g at fixed $V_{ds} = -0.8$ V are plotted in **Figure 5**. The maximum normalized transconductance ($g_{max}^* = g_{max}L/Wd$) exhibited $g_{max}^* = 1.99, 1.85, 1.68$ and 1.39 mS.cm⁻¹ values, while the threshold voltage (V_{th}) obtained from the x-axis interception exhibited $-V_{th} = 0.39, 0.46, 0.52$, and 0.55 V values for $V_{ds} = -1.0, -0.8, -0.6$ and -0.4 V, respectively. For $n = 12$ above c.m.c., the output and transfer characteristics exhibited about ten times lower $-I_{ds}$ values compared with $n = 10$ above c.m.c., as also observed in the $-I_{ds}$ vs concentration plots depicted in the left panel of **Figure 3**.

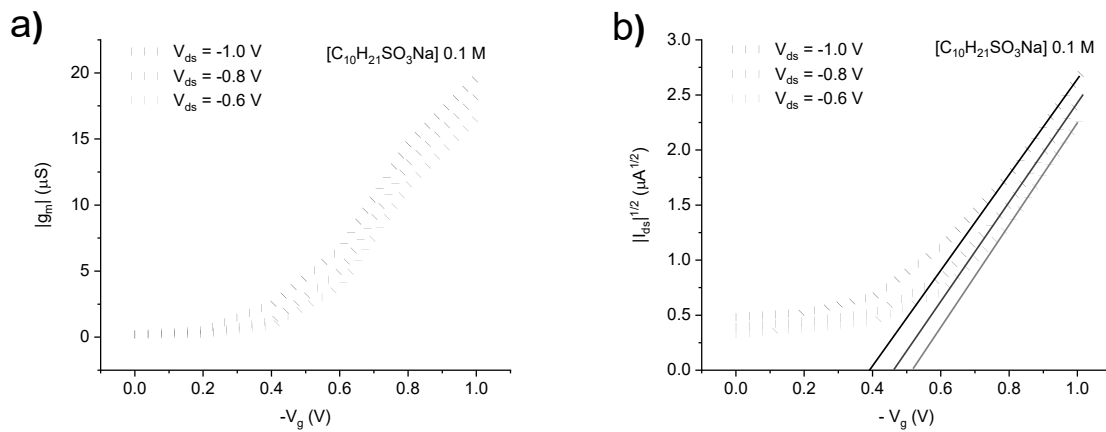


Figure 5 – a) Transconductance (g_m vs V_g at selected V_{ds} values) and **b)** threshold voltage ($|I_{ds}|^{1/2}$ vs V_g at selected V_{ds} values) plots for P3HT-based OECT working with $[C_{10}H_{21}SO_3Na]$ 0.1 M electrolyte at 25 °C.

For instance, $n = 12$ above c.m.c. exhibited $-I_{ds,V_g=-1.0V}$ values ranging from 0.55, 0.44 and 0.35 μA and ON/OFF ratios (estimated using the $-I_{ds,V_g=-1.0V}/-I_{ds,V_g=0.0V}$ ratio) ranging from 1.3, 1.4, 1.5 for $V_{ds} = -1.0, -0.8$ and -0.6 V, respectively, as depicted in **Figure S4**. To provide insights into the ionic transport, injection and ionic-electronic charge transfer properties of these P3HT-based OECT devices, we performed impedance spectroscopy studies. The total impedance (Z) response can be defined as a function of the real part (Z') and the imaginary part (Z'') of impedance, as follows:

$$Z = Z' - iZ''$$

The Nyquist plots ($-Z''$ vs. Z') and the Bode plots (ϕ vs f and $|Z|$ vs f) at the OFF ($V_{g,dc} = 0.0$ V) and ON ($V_{g,dc} = -1.0$ V) modes for $n = 10$ and 12 are depicted in **Figure 6** and **Figure S5**, respectively. The volumetric capacitance (C^*) can be estimated from the plateau observed at low frequencies for the total capacitance response but, in our case, the presence of a small deviation at low frequencies indicates a non-ideal behavior which is more appropriate to study using a circuit model fitting.⁵⁸ Our impedance data showed best fitting with a circuit model based on a resistor (R_{ion}) (representing the electrolyte transport in solution) connected in series with the parallel combination of resistor – diffusive-like constant phase element and capacitive-like constant phase element (R_{ct}/CPE) (representing the electrolyte diffusion and charge transfer processes), as depicted in **Figure S6**. The constant phase element (CPE) impedance can be described by the following equation:

$$Z_{CPE} = (1/Q)/(i\omega)^\alpha$$

where Q (admittance at $\omega = 1$ rad/s) and α (exponent) are frequency-independent parameters, with $\alpha = 1$ and 0 representing an ideal capacitor and resistor, respectively, while $\alpha = 0.5$ is associated with diffusion processes.⁵⁹ The fitted bulk solution ionic resistance (R_{ion}) values were $8.83 \pm 0.15/8.74 \pm 0.15$ k Ω ($n = 10$) and $32.51 \pm 0.54/37.16 \pm 0.61$ k Ω ($n = 12$) for ON/OFF modes, respectively. The similarity between both values is quite expected considering that the micelles are at the same concentration. On the other hand, the fitted charge transfer resistance (R_{ct}) values were $803 \pm 68/1579 \pm 211$ k Ω ($n = 10$) and $426 \pm 166/578 \pm 117$ k Ω ($n = 12$) and the non-ideal capacitor constant phase element (Q_{CPE}) values were $15.1 \pm 1.2/28.5 \pm 1.3$ nS.s $^\alpha$ ($n = 10$) and $59.2 \pm 6.4/130 \pm 14$ nS.s $^\alpha$ ($n = 12$) with $\alpha \sim 0.8$ for ON/OFF modes, respectively.

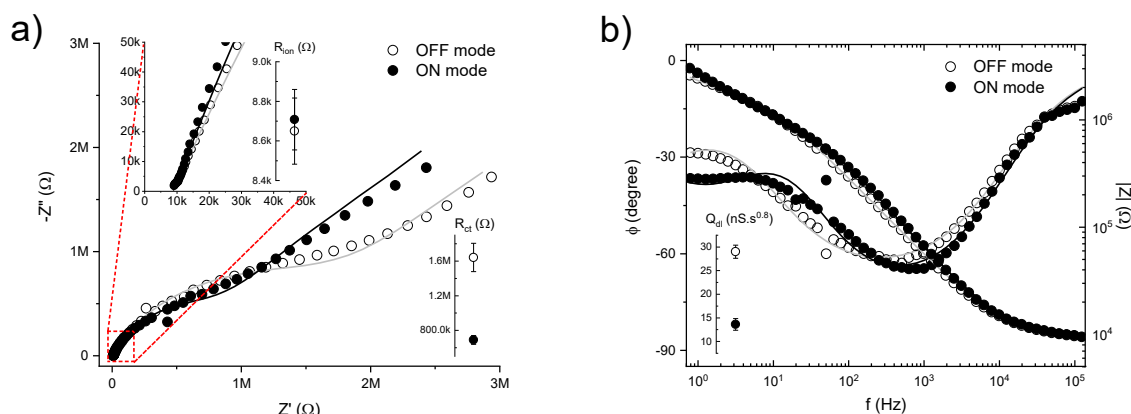


Figure 6 – a) Nyquist and b) Bode plots for P3HT-based OECT working with $[C_{10}H_{21}SO_3Na]$ 0.1 M electrolyte at 25 °C for different operation modes; *i.e.* OFF ($V_{g,dc} = 0.0$ V) and ON ($V_{g,dc} = -1.0$ V).

The decrease in the charge transfer resistance and pseudo-capacitance clearly indicates that the negative gate voltage induces interesting molecular rearrangements at the interface. These results allow us to consider some scenarios to understand the charge transfer processes at the interface between the amphiphilic electrolyte monolayer and the conductive polymer comprising the OECT channel. A possible scenario implies that, in the absence of any gate voltage, the amphiphilic electrolyte monolayer is formed at the interface with the sulfonate heads exposed to the aqueous medium and the hydrophobic alkyl chains interacting with the hydrophobic P3HT polymer. Then, in the presence of a sufficiently strong negative gate voltage (*e.g.* $V_g = -1.0$ V), not only the sodium counterions ejected from the interface, but also the amphiphilic molecules from the monolayer probably synchronously reverse their orientation and get injected into the P3HT region, as depicted in **Figure 7**. This scenario implies that the monolayer can be reversed completely or partially, but this synchronous reversion enhances the interaction of sulfonate groups with thiophene rings, inducing the doping of P3HT and thus the enhancement in the channel current, as is well understood in the literature.⁶⁰ It is noteworthy to note that the response of amphiphilic species with lower c.m.c. values (such as $n = 12$ alkyl sulfonates) are much poorer than those with higher c.m.c. values (such as $n = 10$ alkyl sulfonates).

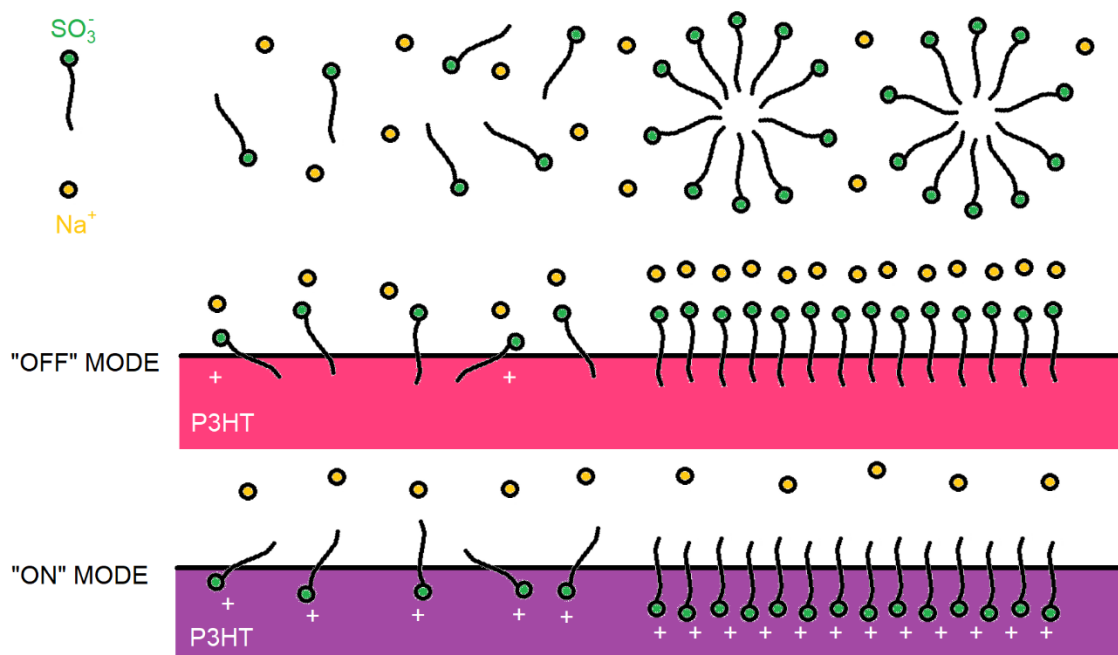


Figure 7 – Schematization of the formation of a monolayer in the electrolyte/P3HT interface above the critical micelle concentration and its effect on the “OFF” and “ON” states for P3HT-based OECT.

This could be related to the formation of more condensed monolayers compared to the more expanded monolayers formed by amphiphilic species with higher and lower c.m.c. values, respectively.⁶¹ Below the critical micelle concentration, there is only a diluted and isolated interaction of the amphiphilic species sulfonate groups with P3HT and thus the OECT response enhancement is expected to be less pronounced. This can be associated with the surface adsorption of sulfonate ions near the P3HT interface, even in the absence of severe penetration into the bulk film, which could produce electrostatic doping effects via local field modulation. In addition, the increase in ionic strength with increasing surfactant concentration may also enhance electrochemical coupling, screening effects, or double-layer capacitance at the interface, thus yielding less pronounced enhancement on the OECT response.

Conclusions

In the present report, we present a proof-of-concept approach to study the effect of critical micelle concentration on the amphiphilic species response using organic electrochemical transistors working in the accumulation mode. First of all, by using our OECT devices, we estimate the critical micelle concentration of alkyl sulfonate amphiphilic species, yielding quite similar values compared to bulk solution conductivity experiments reported in the literature. Above the critical micelle concentration, the OECT devices working with n-alkyl sulfonates ($n = 12$) yielded ON/OFF ratios of 30 – 60, maximum normalized transconductance of $g_{\text{max}}^* = 1.99 - 1.39 \text{ mS.cm}^{-1}$ and threshold voltage of $-V_{\text{th}} = 0.39 - 0.55 \text{ V}$ at $V_g = -1.0 \text{ V}$. Our impedance spectroscopy studies performed at ON and OFF modes suggested that, in the presence of a sufficiently strong negative gate voltage ($V_g = -1.0 \text{ V}$), not only the sodium counterions are ejected from the interface, but also the amphiphilic molecules from the monolayer probably synchronously reverse their orientation and get injected into the P3HT region. Our results indicate that OECT devices represent a promising platform to estimate the critical micelle concentration of amphiphilic species, but also to study the formation of amphiphilic monolayers of more complex systems of biological interest.

Data availability

The data supporting this article have been included as part of the Supplementary Information.

Author Contributions

The manuscript was written through the contributions of all authors. All authors have given approval to the final version of the manuscript.

Acknowledgments

The authors thank the Uruguayan CSIC, ANII, and PEDECIBA funding institutions. We also appreciate the financial support of ANII POS_NAC_2024_1_183297 PhD grant.

References

- (1) Rivnay, J.; Inal, S.; Salleo, A.; Owens, R. M.; Berggren, M.; Malliaras, G. G. Organic electrochemical transistors. *Nat. Rev. Mater.* 2018, 3, 17086.
- (2) Khodagholy, D.; Rivnay, J.; Sessolo, M.; Gurfinkel, M.; Leleux, P.; Jimison, L. H.; Stavriniidou, E.; Herve, T.; Sanaur, S.; Owens, R. M.; Malliaras, G. G. High transconductance organic electrochemical transistors. *Nat. Commun.* 2013, 4, 2133.
- (3) Bießmann, L.; Kreuzer, L. P.; Widmann, T.; Hohn, N.; Moulin, J. F.; Müller-Buschbaum, P. Monitoring the Swelling Behavior of PEDOT:PSS Electrodes under High Humidity Conditions. *ACS Appl. Mater. Interfaces* 2018, 10, 9865–9872.
- (4) Romero, M.; Mombrú, D.; Pignanelli, F.; Faccio, R.; Mombrú, A. W. Mixed Ionic-Electronic Transport for PEDOT:PSS-Based Zero-Gated Organic Electrochemical Transistors Using Impedance Spectroscopy and Micro-Raman Imaging. *ACS Appl. Electron. Mater.* 2023, 5, 9, 4863–4874.
- (5) Inal, S.; Rivnay, J.; Leleux, P.; Ferro, M.; Ramuz, M.; Brendel, J. C.; Schmidt, M. M.; Thelakkat, M.; Malliaras, G. G. A High Transconductance Accumulation Mode Electrochemical Transistor. *Adv. Mater.* 2014, 26 (44), 7450–7455.
- (6) Wagner, J., Song, Y., Lee, T. & Katz, H.E. (2022). The combined influence of polythiophene side chains and electrolyte anions on organic electrochemical transistors. *Electrochem. Sci. Adv.*, 2, 2100165.
- (7) E. Macchia, K. Manoli, B. Holzer, C. Di Franco, M. Ghittorelli, F. Torricelli, D. Alberga, G. F. Mangiatordi, G. Palazzo, G. Scamarcio, L. Torsi, *Nat. Commun.* 2018, 9, 3223.
- (8) P. Seshadri, K. Manoli, N. Schneiderhan-Marra, U. Anthes, P. Wierchowicz, K. Bonrad, C. Di Franco, L. Torsi, *Biosens. Bioelectron.* 2018, 104, 113.
- (9) S. P. White, C. D. Frisbie, K. D. Dorfman, *ACS Sens.* 2018, 3, 395. 12.4 E. Macchia, K. Manoli, B. Holzer, C. Di Franco, R. A. Picca, N. Cioffi, G. Scamarcio, G. Palazzo, L. Torsi, *Anal. Bioanal. Chem.* 2019, 411, 4899.
- (10) E. Macchia, L. Sarcina, R. A. Picca, K. Manoli, C. Di Franco, G. Scamarcio, L. Torsi, *Anal. Bioanal. Chem.* 2020, 412, 811.
- (11) L. Sarcina, F. Viola, F. Modena, R. A. Picca, P. Bollella, C. Di Franco, N. Cioffi, M. Caironi, R. Osterbacka, I. Esposito, G. Scamarcio, L. Torsi, F. Torricelli, E. Macchia, *Anal. Bioanal. Chem.* 2022, 414, 5657.
- (12) L. Sarcina, E. Macchia, G. Loconsole, G. D’Attoma, P. Bollella, M. Catacchio, F. Leonetti, C. Di Franco, V. Elicio, G. Scamarcio, G. Palazzo, D. Boscia, P. Saldarelli, L. Torsi, *Adv. Sci.* 2022, 9, 2203900.
- (13) Huang, L., Wang, Z., Chen, J., Wang, B., Chen, Y., Huang, W., Chi, L., Marks, T.J. & Facchetti, A. (2021). Porous Semiconducting Polymers Enable High-Performance Electrochemical Transistors. *Adv. Mater.*, 33, 2007041.

464 (14) Tung, Y.H., Li, C.Y., Huang, Y.C. & Lin Y.C. (2025). Strategically Tailoring Porous
 465 Polythiophene Nanofibers in Organic Electrochemical Transistors To Facilitate the Anion
 466 Doping. *ACS Electrochem.*, 1(7), 1164–1175.

467 (15) Song, J., Liu, H., Zhao, Z., Lin, P., & Yan, F. (2024). Flexible organic transistors for biosensing:
 468 devices and applications. *Advanced Materials*, 36(20), 2300034.

469 (16) Liu, H., Song, J., Zhao, Z., Zhao, S., Tian, Z., & Yan, F. (2024). Organic electrochemical
 470 transistors for biomarker detections. *Advanced Science*, 11(27), 2305347.

471 (17) Flagg, L. Q., Giridharagopal, R., Guo, J., & Ginger, D. S. (2018). Anion-dependent doping
 472 and charge transport in organic electrochemical transistors. *Chemistry of Materials*, 30(15),
 473 5380-5389.

474 (18) Flagg, L. Q., Bischak, C. G., Quezada, R. J., Onorato, J. W., Luscombe, C. K., & Ginger, D. S.
 475 (2020). P-type electrochemical doping can occur by cation expulsion in a high-performing
 476 polymer for organic electrochemical transistors. *ACS Materials Letters*, 2(3), 254-260.

477 (19) Zhang, Y., Wang, Y., Qing, X., Wang, Y., Zhong, W., Wang, W., Chen, Y., Liu, Q., & Wang, D.
 478 (2020). Fiber organic electrochemical transistors based on multi-walled carbon nanotube and
 479 polypyrrole composites for noninvasive lactate sensing. *Analytical and Bioanalytical*
 480 *Chemistry*, 412, 7515-7524.

481 (20) Pappa, A. M., Ohayon, D., Giovannitti, A., Maria, I. P., Savva, A., Uguz, I., Rivnay, J.,
 482 McCulloch, I., Owens, R., & Inal, S. (2018). Direct metabolite detection with an n-type
 483 accumulation mode organic electrochemical transistor. *Science advances*, 4(6), eaat0911.

484 (21) Braendlein, M., Pappa, A. M., Ferro, M., Lopresti, A., Acquaviva, C., Mamessier, E.,
 485 Malliaras, G., & Owens, R. M. (2017). Lactate detection in tumor cell cultures using organic
 486 transistor circuits. *Adv. Mater.*, 29(13), 1605744.

487 (22) Zhang, L., Wang, G., Wu, D., Xiong, C., Zheng, L., Ding, Y., Lu, H., Zhang, G., & Qiu, L. (2018).
 488 Highly selective and sensitive sensor based on an organic electrochemical transistor for the
 489 detection of ascorbic acid. *Biosensors and Bioelectronics*, 100, 235-241.

490 (23) Zhu, R., Wang, Y., Tao, Y., Wang, Y., Chen, Y., Li, M., Liu, Q., Yang, L. & Wang, D. (2022).
 491 Layer-by-layer assembly of composite conductive fiber-based organic electrochemical
 492 transistor for highly sensitive detection of sialic acid. *Electrochimica Acta*, 425, 140716.

493 (24) Chen, L., Wang, N., Wu, J., Yan, F., & Ju, H. (2020). Organic electrochemical transistor for
 494 sensing of sialic acid in serum samples. *Analytica Chimica Acta*, 1128, 231-237.

495 (25) Guo, X., Liu, J., Liu, F., She, F., Zheng, Q., Tang, H., Ma, M., & Yao, S. (2017). Label-free and
 496 sensitive sialic acid biosensor based on organic electrochemical transistors. *Sensors and*
 497 *Actuators B: Chemical*, 240, 1075-1082.

498 (26) Yang, A., Li, Y., Yang, C., Fu, Y., Wang, N., Li, L., & Yan, F. (2018). Fabric organic
 499 electrochemical transistors for biosensors. *Advanced Materials*, 30(23), 1800051.

500 (27) Galliani, M., Diacci, C., Berto, M., Sensi, M., Beni, V., Berggren, M., Borsari, M., Simon, D.,
 501 Biscarini, F., & Bortolotti, C. A. (2020). Flexible printed organic electrochemical transistors for
 502 the detection of uric acid in artificial wound exudate. *Advanced Materials Interfaces*, 7(23),
 503 2001218.

504 (28) Tao, Y., Wang, Y., Zhu, R., Chen, Y., Liu, X., Li, M., Yang, L., Wang, Y. & Wang, D. (2022).
 505 Fiber based organic electrochemical transistor integrated with molecularly imprinted
 506 membrane for uric acid detection. *Talanta*, 238, 123055.

507 (29) Saraf, N., Woods, E. R., Peppler, M., & Seal, S. (2018). Highly selective aptamer based
 508 organic electrochemical biosensor with pico-level detection. *Biosensors and*
 509 *Bioelectronics*, 117, 40-46.

510 (30) Coppedè, N., Tarabella, G., Villani, M., Calestani, D., Iannotta, S., & Zappettini, A. (2014).
 511 Human stress monitoring through an organic cotton-fiber biosensor. *Journal of Materials*
 512 *Chemistry B*, 2(34), 5620-5626.

513 (31) Mak, C. H., Liao, C., Fu, Y., Zhang, M., Tang, C. Y., Tsang, Y. H., Chan, H. L. W. & Yan, F.
 514 (2015). Highly-sensitive epinephrine sensors based on organic electrochemical transistors
 515 with carbon nanomaterial modified gate electrodes. *Journal of materials chemistry C*, 3(25),
 516 6532-6538.

517 (32) Wang, N., Liu, Y., Fu, Y., & Yan, F. (2018). AC measurements using organic electrochemical
 518 transistors for accurate sensing. *ACS applied materials & interfaces*, 10(31), 25834-25840.

519 (33) Qing, X., Wang, Y., Zhang, Y., Ding, X., Zhong, W., Wang, D., Wang, W., Liu, Q., Liu, K., Li,
 520 M., & Lu, Z. (2019). Wearable fiber-based organic electrochemical transistors as a platform for
 521 highly sensitive dopamine monitoring. *ACS applied materials & interfaces*, 11(14), 13105-
 522 13113.

523 (34) Fenoy, G. E., Von Bilderling, C., Knoll, W., Azzaroni, O., & Marmisollé, W. A. (2021). PEDOT:
 524 Tosylate-Polyamine-Based Organic Electrochemical Transistors for High-Performance
 525 Bioelectronics. *Advanced Electronic Materials*, 7(6), 2100059.

526 (35) Macchia, E., Manoli, K., Holzer, B., Di Franco, C., Ghittorelli, M., Torricelli, F., Alberga, D.,
 527 Mangiatordi, G. F., Pallazo, G., Scamarcio, G. & Torsi, L. (2018). Single-molecule detection with
 528 a millimetre-sized transistor. *Nature Communications*, 9(1), 3223.

529 (36) Seshadri, P., Manoli, K., Schneiderhan-Marra, N., Anthes, U., Wierchowicz, P., Bonrad, K.,
 530 Di Franco, C., & Torsi, L. (2018). Low-picomolar, label-free procalcitonin analytical detection
 531 with an electrolyte-gated organic field-effect transistor based electronic
 532 immunosensor. *Biosensors and Bioelectronics*, 104, 113-119.

533 (37) Peng, J., He, T., Sun, Y., Liu, Y., Cao, Q., Wang, Q., & Tang, H. (2018). An organic
 534 electrochemical transistor for determination of microRNA21 using gold nanoparticles and a
 535 capture DNA probe. *Microchimica Acta*, 185, 1-8.

(38) Song, Y., Zhang, H., Mukhopadhyaya, T., Hall, A. S., & Katz, H. E. (2022). Sensitive organic electrochemical transistor biosensors: Comparing single and dual gate functionalization and different COOH-functionalized bioreceptor layers. *Biosensors and Bioelectronics*, 216, 114691.

(39) Salvigni, L., Mariani, F., Gualandi, I., Decataldo, F., Tessarolo, M., Tonelli, D., Fraboni, B., & Scavetta, E. (2023). Selective detection of liposoluble vitamins using an organic electrochemical transistor. *Sensors and Actuators B: Chemical*, 393, 134313.

(40) Muller, P. (1994). Glossary of terms used in physical organic chemistry (IUPAC Recommendations 1994). *Pure and applied chemistry*, 66(5), 1077-1184.

(41) P. Mukerjee and K.J. Mysels, Critical micelle concentrations of aqueous surfactant systems, NSRDS-NBS 36, National Bureau of Standards, 1971.

(42) Paruchuri, V., Nguyen, A. V., & Miller, J. D. (2004). Zeta-potentials of self-assembled surface micelles of ionic surfactants adsorbed at hydrophobic graphite surfaces. *Colloids and Surfaces A: Physicochem. Eng. Aspects*, 250, 519-526.

(43) Lu, Z., van Niekerk, D., Savva, A., Kallitsis, K., Thiburce, Q., Salleo, A., Pappa, A. M., & Owens, R. M. (2022). Understanding electrochemical properties of supported lipid bilayers interfaced with organic electronic devices. *Journal of Materials Chemistry C*, 10(20), 8050-8060.

(44) Bali, K., Guffick, C., McCoy, R., Lu, Z., Kaminski, C. F., Mela, I., Owens, R., & van Veen, H. W. (2023). Biosensor for Multimodal Characterization of an Essential ABC Transporter for Next-Generation Antibiotic Research. *ACS Applied Materials & Interfaces*, 15(10), 12766-12776.

(45) Lu, Z., Barberio, C., Fernandez-Villegas, A., Withers, A., Wheeler, A., Kallitsis, K., Martinelli, E., Savva, A., Hess, B. M., Pappa, A. M., Kaminski Schierle, G. S., & Owens, R. M. (2024). Microelectrode Arrays Measure Blocking of Voltage-Gated Calcium Ion Channels on Supported Lipid Bilayers Derived from Primary Neurons. *Advanced Science*, 11(27), 2304301.

(46) Nguy, T. P., Hayakawa, R., Kilinc, V., Petit, M., Yemineni, S. N., Higuchi, M., Raimundo, J. M., Charrier, A. M. & Wakayama, Y. (2020). Electrolyte-gated-organic field effect transistors functionalized by lipid monolayers with tunable pH sensitivity for sensor applications. *Applied Physics Express*, 13(1), 011005.

(47) Nguy, T. P., Kilinc, V., Hayakawa, R., Henry-De-Villeneuve, C., Raimundo, J. M., Wakayama, Y., & Charrier, A. (2022). Affinity driven ion exchange EG-OFET sensor for high selectivity and low limit of detection of cesium in seawater. *Sensors and Actuators B: Chemical*, 351, 130956.

(48) Jonathan Rivnay, Pierre Leleux, Marc Ferro, Michele Sessolo, Adam Williamson, Dimitrios A. Koutsouras, Dion Khodagholy, Marc Ramuz, Xenofon Strakosas, Roisin M. Owens, Christian Benar, Jean-Michel Badier, Christophe Bernard, and George G. Malliaras. High-performance transistors for bioelectronics through tuning of channel thickness. *Sci. Adv.* 2015;1:e1400251.

(49) Anastasios G. Polyravas, Nathan Schaefer, Vincenzo F. Curto, Andrea Bonaccini Calia, Anton Guimera-Brunet, Jose A. Garrido, and George G. Malliaras. Effect of channel thickness on noise in organic electrochemical transistors. *Appl. Phys. Lett.* 117, 073302 (2020).

574 (50) Chaoyi Yan, Lanyi Xiang, Yu Xiao, Xuefeng Zhang, Ziling Jiang, Boya Zhang, Chenyang Li,
 575 Siyu Di & Fengjiao Zhang. Lateral intercalation-assisted ionic transport towards high-
 576 performance organic electrochemical transistor. (2024) *Nature Communications* 15:10118.

577 (51) Yan, P., & Xiao, J. X. (2004). Polymer–surfactant interaction: differences between alkyl
 578 sulfate and alkyl sulfonate. *Colloids and Surfaces A: Physicochemical and Engineering*
 579 *Aspects*, 244(1-3), 39-44.

580 (52) Werzer, O., & Resel, R. (2013). Model-independent X-ray reflectivity fitting for structure
 581 analysis of poly (3-hexylthiophene) films. *Macromolecules*, 46(9), 3529-3533.

582 (53) Yasaka, M. (2010). X-ray thin-film measurement techniques. *The Rigaku Journal*, 26(2), 1-
 583 9.

584 (54) Pappa, A.-M.; Ohayon, D.; Giovannitti, A.; Maria, I.; Savva, A.; Uguz, I.; Rivnay, J.;
 585 McCulloch, I.; Owens, R.; Inal, S. Direct Metabolite Detection with an N-Type Accumulation
 586 Mode Organic Electrochemical Transistor. *Sci. Adv.* 2018, 4, eaat0911.

587 (55) Giovannitti, A.; Sbircea, D.-T.; Inal, S.; Nielsen, C. B.; Bandiello, E.; Hanifi, D. A.; Sessolo,
 588 M.; Malliaras, G. G.; McCulloch, I.; Rivnay, J. Controlling the Mode of Operation of Organic
 589 Transistors through Side-Chain Engineering. *Proc. Natl. Acad. Sci.* 2016, 113, 12017–12022.

590 (56) Giovannitti, A.; Thorley, K. J.; Nielsen, C. B.; Li, J.; Donahue, M. J.; Malliaras, G. G.; Rivnay,
 591 J.; McCulloch, I. Redox-Stability of Alkoxy-BDT Copolymers and Their Use for Organic
 592 Bioelectronic Devices. *Adv. Funct. Mater.* 2018, 28, 1706325.

593 (57) Bisquert, J.; Ilyassov, B.; Tessler, N. (2024). Switching Response in Organic Electrochemical
 594 Transistors by Ionic Diffusion and Electronic Transport. *Adv. Sci.* 11, 2404182.

595 (58) Ohayon, D., Druet, V., & Inal, S. (2023). A guide for the characterization of organic
 596 electrochemical transistors and channel materials. *Chemical Society Reviews*, 52(3), 1001-
 597 1023.

598 (59) Orazem, M. E., & Tribollet, B. (2008). Electrochemical Impedance Spectroscopy. *New*
 599 *Jersey*, 1(906), 383-389. Chapter 11, Diffusion Impedance, Pages: 183-210.

600 (60) Mombrú, D., Romero, M., Faccio R., Mombrú, A.W. (2020) Unraveling the lithium bis
 601 (trifluoromethanesulfonyl) imide (LiTFSI) doping mechanism of regioregular poly (3-
 602 hexylthiophene): experimental and theoretical study. *The Journal of Physical Chemistry C* 124
 603 (13), 7061-7070.

604 (61) Peltonen, L.; Hirvonen, J.; Yliruusi, J. (2001) The Effect of Temperature on Sorbitan
 605 Surfactant Monolayers. *Journal of Colloid and Interface Science* 239, 1, 134-138.